

Masonite Beams AB  
Tommy Persson  
Box 5  
914 29 RUNDVIK

## Emission measurements after 28 days

(2 appendices)

### Object

One sample of a wood-based beam was delivered to RISE by the customer.

|                          |                                      |
|--------------------------|--------------------------------------|
| Product name:            | <b>H300 OSB</b>                      |
| Production date:         | 2018-03-05                           |
| Size of sample:          | 1.0 x 0.3 m, wrapped in plastic foil |
| Date of sampling:        | 2018-03-05                           |
| Date of arrival to RISE: | 2018-03-16                           |
| Date of analysis:        | week 12 - 18, 2018                   |

### Assignment

Emission measurement according to ISO 16000-9:2006 (Indoor air – Part 9: Determination of the emission of volatile organic compounds from building products and furnishing – Emission test chamber method), after 28 days regarding volatile organic compounds (VOC and VVOC/SVOC), carcinogenic substances (VOC-substances, EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), formaldehyde and acetaldehyde (ISO 16000-3:2011). Evaluation according to EN 16516:2017 (EU-LCI values).

For evaluation of test results the principle of shared risk is applied, i.e. for a max limit ( $\leq$ ) a result  $\leq$  the limit complies and a result  $>$  the limit does not comply (ILAC G8 section 2.7).

### Method

The test was started 2018-03-21 by unwrapping the test sample. Short edges were sealed with aluminium tape. The specimen was placed in a separate conditioning container (with air velocity of ca 0.2 m/s) in a room with controlled climate conditions of  $23 \pm 2$  °C and  $50 \pm 5$  % RH. The test specimen was placed into the chamber five days prior to air samplings. Air samplings after 28 days of conditioning were carried out on 2018-04-18.

### RISE Research Institutes of Sweden AB

|                                      |                                   |   |
|--------------------------------------|-----------------------------------|---|
| Postal address                       | Office location                   | Phone / Fax / E-mail                              |
| Box 857<br>SE-501 15 BORÅS<br>Sweden | Brinellgatan 4<br>SE-504 62 BORÅS | +46 10 516 50 00<br>+46 33 13 55 02<br>info@ri.se |

This report may not be reproduced other than in full, except with the prior written approval of the issuing laboratory.

Test conditions in the chamber:

|                                   |  |
|-----------------------------------|--|
| Chamber volume:                   | 1.0 m <sup>3</sup>                     |
| Temperature:                      | 23 ± 0.5 °C                            |
| Relative humidity:                | 50 ± 5 % RH                            |
| Surface area of test specimen:    | 0.69 m <sup>2</sup>                    |
| Air exchange rate:                | 0.5 h <sup>-1</sup>                    |
| Area specific air flow rate:      | 0.72 m <sup>3</sup> /m <sup>2</sup> h. |
| Air velocity at specimen surface: | 0.1 – 0.3 m/s                          |

Tenax TA was used as adsorption medium for VOC. The tubes were thermally desorbed and analysed in accordance to RISE method 0601, similar to ISO 16000-6:2011 (Determination of volatile organic compounds in indoor and test chamber air by active sampling on Tenax TA sorbent, thermal desorption and gas chromatography using MS/FID). This means an analysis in a gas chromatograph and detection with a flame ionisation detector (FID) and mass selective detector (MS). The capillary column used is coated with 5% phenyl/ 95 % methylpolysiloxane. The FID signals are used for compound quantification. The total volatile organic compounds (TVOC) means compounds eluting between and including n-hexane to hexadecane, having boiling points in the range of about 70-260 °C. Minimum duplicate air samples were taken and the results are mean values. Sampled volumes are 3 to 7 L.

Tenax TA was also used as adsorption medium for testing of volatile carcinogenic compounds according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), (exclusive formaldehyde), 1 µg/m<sup>3</sup> and above.

The samplings of aldehydes were carried out with DNPH samplers. The samplers were analysed according to RISE method 2302, similar to ISO 16000-3:2011 (Indoor air - Part 3: Determination of formaldehyde and other carbonyl compounds – Active sampling method). This means analysis on a liquid chromatograph with absorbance detector. Duplicate air samples were taken and the results are mean values. Sampled volumes were 60 to 120 L.

## Results

The results in Table 1 are expressed as area specific emission rates and as concentrations in a reference room (according to EN 16516:2017). The reference room has a base area of 3 m x 4 m and a height of 2.5 m, with an air exchange rate of 0.5 h<sup>-1</sup>. The wall area is 31.4 m<sup>2</sup>, floor area is 12 m<sup>2</sup>, small area, like a door, is 1.6 m<sup>2</sup> and very small area, like sealant, is 0.2 m<sup>2</sup>. **Small area** is used for the calculation of the concentrations.

Calculation of the concentration from the emission rate:

$$C = \frac{E_a \times A}{n \times V}$$

C = concentration of VOC in the reference room, in µg/m<sup>3</sup>  
 E<sub>a</sub> = area specific emission rate, in µg/m<sup>2</sup>h  
 A = surface area of product in reference room, in m<sup>2</sup>  
 n = air exchange rate, in changes per hour, here 0.5 h<sup>-1</sup>  
 V = volume of the reference room, in m<sup>3</sup>, here 30 m<sup>3</sup>

**Table 1.**  
Emission results of **H300 OSB** after 28 days

| Volatile organic compounds                                | CAS number | Retention time (min) | ID <sup>1</sup> | Emission rate (µg/m <sup>2</sup> h) | Concentration in reference room (µg/m <sup>3</sup> ) | LCI <sub>i</sub> (µg/m <sup>3</sup> ) | R <sub>i</sub> (c <sub>i</sub> /LCI <sub>i</sub> ) |
|---|------------|----------------------|-----------------|-------------------------------------|--|---------------------------------------|--|
| <b>TVOC (C<sub>6</sub> – C<sub>16</sub>)</b>              | --         | 6.5 – 38             | B               | 110                                 | < 10   | --                                    | --   |
| <b>Volatile Carcinogens<sup>2</sup></b>                   |            | 6.5 – 38             |                 |                                     |  |                                       |  |
| No substances detected                                    | --         | --                   | B               | < 1                                 | < 1  | --                                    | --   |
| <b>VOC with LCI<sup>3</sup></b>                           |            | 6.5 – 38             |                 |                                     |  |                                       |  |
| Acetic acid (VVOC)  | 64-19-7    | 5.7                  | A               | 31                                  | < 5  | 1200                                  | --   |
| Pentanal  | 110-62-3   | 8.8                  | A               | 12                                  | < 5  | 800                                   | --   |
| 1-Pentanol  | 71-41-0    | 10.8                 | A               | 5                                   | < 5  | 730                                   | --   |
| Hexanal   | 66-25-1    | 12.2                 | A               | 41                                  | < 5  | 900                                   | --   |
| α-Pinene  | 80-56-8    | 17.7                 | A               | 26                                  | < 5  | 2500                                  | --   |
| β-Pinene  | 127-91-3   | 19.4                 | A               | 3                                   | < 5  | 1400                                  | --   |
| 3-Carene  | 13466-78-9 | 20.4                 | A               | 16                                  | < 5  | 1500                                  | --   |
| Limonene  | 138-86-3   | 21.1                 | A               | 2                                   | < 5  | 5000                                  | --   |
| Nonanal   | 124-19-6   | 23.4                 | A               | 7                                   | < 5  | 900                                   | --   |
| <b>∑ VOC with LCI</b>                                     | --         | --                   | A               | 140                                 | < 5  | --                                    | --   |
| <b>VOC without LCI<sup>4</sup></b>                        |            |                      |                 |                                     |  |                                       |  |
| Hexanoic acid   | 142-62-1   | 18.0                 | B               | 10                                  | < 5  | --                                    | --   |
| <b>∑ VOC without LCI</b>                                  | --         | --                   | B               | 10                                  | < 5  | --                                    | --   |
| <b>SVOC (C<sub>16</sub> – C<sub>22</sub>)<sup>5</sup></b> |            | 38 - 51              |                 |                                     |  |                                       |  |
| No substances detected                                    | --         | --                   | B               | < 2                                 | < 5  | --                                    | --   |
| <b>∑ SVOC</b>   | --         | --                   | B               | < 2                                 | < 5  | --                                    | --   |
| <b>VVOC (&lt; C<sub>6</sub>)<sup>6</sup></b>              |            | 4.9 – 6.5            |                 |                                     |  |                                       |  |
| Formaldehyde <sup>7</sup>                                 | 50-00-0    | --                   | A               | 17                                  | < 5  | 100                                   | --   |
| Acetaldehyde <sup>7</sup>                                 | 75-07-0    | --                   | A               | 8                                   | < 5  | 1 200                                 | --   |
| <b>∑ VVOC</b>   | --         | --                   | A               | 25                                  | < 5  | --                                    | --   |
| <b>R = ∑ C<sub>i</sub> / LCI<sub>i</sub><sup>8</sup></b>  | --         | --                   | --              | --                                  | --   | --                                    | < 0.01   |

<sup>1</sup>) ID: A = quantified compound specific, B = quantified as toluene-equivalent

<sup>2</sup>) Volatile carcinogens = VOCs according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B

<sup>3</sup>) VOC with LCI = identified VOC-compound with LCI-value according to EU-LCI, Dec 2016

<sup>4</sup>) VOC without LCI = VOC-compound without LCI-value or not identified.

<sup>5</sup>) SVOC = semi-volatile organic compounds, as defined in ISO 16000-6 (not part of accreditation)

<sup>6</sup>) VVOC = very volatile organic compounds, as defined in ISO 16000-6 (not part of accreditation)

<sup>7</sup>) VVOC-aldehydes measured with DNPH samplers (ISO 16000-3)

<sup>8</sup>) All VVOC, VOC, SVOC and carcinogens with LCI

Only VOC-compounds with an emission rate higher than  $5 \mu\text{g}/\text{m}^2\text{h}$  are listed in Table 1, carcinogenic compounds  $\geq 1 \mu\text{g}/\text{m}^2\text{h}$ . Only the compounds with a concentration in the reference room  $> 5 \mu\text{g}/\text{m}^3$  are evaluated based on LCI (= lowest concentration of interest). TVOC expressed in  $\mu\text{g}/\text{m}^3$  is the sum of all individual substances with concentrations  $\geq 5 \mu\text{g}/\text{m}^3$  (in toluene equivalents). The emission rate of TVOC ( $\mu\text{g}/\text{m}^2\text{h}$ ) includes all compounds  $\text{ca} \geq 1 \mu\text{g}/\text{m}^2\text{h}$  in the chamber.

Quantification limit for TVOC is  $10 \mu\text{g}/\text{m}^2\text{h}$ . Measurement uncertainty for VOC is 15 % (rel) and for formaldehyde 30 % (rel). Background of TVOC in the empty chamber was below  $20 \mu\text{g}/\text{m}^3$  and is subtracted.

See Appendix 1 for a gas chromatogram (FID spectra) and Appendix 2 for a photo of the test specimen.

## Summary of the test results

The test results are summarized in Table 2.

**Table 2.**

Summary of the emission results after 28 days of **H300 OSB**

| Compounds                     | Emission rate<br>( $\mu\text{g}/\text{m}^2\text{h}$ ) | Concentration in<br>reference room<br>(small area scenario)<br>( $\mu\text{g}/\text{m}^3$ ) |
|-------------------------------|---|---|
| TVOC                          | 110   | < 10  |
| $\sum$ Carcinogenic VOCs      | < 1   | < 1   |
| $\sum$ VOC with LCI           | 140   | < 5   |
| $\sum$ VOC without LCI        | 10  | < 5   |
| $\sum$ VVOC                   | 25  | < 5   |
| Formaldehyde                  | 17  | < 5   |
| $\sum$ SVOC                   | < 2   | < 5   |
| $R = \sum C_i / \text{LCI}_i$ | < 0.01  |   |

The emission result of **formaldehyde** ( $17 \mu\text{g}/\text{m}^2\text{h}$ ) can be converted into a concentration according to EN 717-1:2004 (Wood-based panels – Determination of formaldehyde release – Part 1: Formaldehyde emission by the chamber method).

In EN 717-1 the area specific air flow rate is  $1 \text{ m}^3/\text{m}^2\text{h}$ , this means that the concentration equals the emission rate. After adjustment of measuring at different relative humidity (division by 1.09 (ASTM E 1333-96)) the emission of formaldehyde of the tested product expressed as **concentration according to EN 717-1 is  $0.016 \text{ mg}/\text{m}^3$**  (670 h\*). \*<sup>1</sup> The duration of the test in hours.

## Evaluation of the test results

The test results are compared to the emission requirements in section O32 and O33 of Nordic Ecolabelling for Construction and facade panels, version 6.3, 21 June 2016.

**Table 3.**

The test results are compared to the requirements of wood based with surface treatment

| Compounds                                | Limit value after<br>28 days<br>(mg/m <sup>3</sup> ) | Test Results<br>(mg/m <sup>3</sup> ) | Pass / Fail |
|--|--|--------------------------------------|-------------|
| TVOC (C <sub>6</sub> -C <sub>16</sub> )  | 0.30   | < <b>0.010</b>                       | <b>PASS</b> |
| SVOC (C <sub>16</sub> -C <sub>23</sub> ) | 0.10   | < <b>0.005</b>                       | <b>PASS</b> |
| Formaldehyde (EN 717-1)                  | 0.07   | <b>0.016</b>                         | <b>PASS</b> |

The test results are in compliance with the requirements of Nordic Ecolabelling for Construction and facade panels.

### RISE Research Institutes of Sweden AB Chemistry and Materials - Chemistry

Performed by

Examined by

Maria Rådemar

Tove Malin

### Appendices


1. Gas Chromatogram
2. Photo of the test specimen

Appendix 1

Gas chromatogram

H300 OSB, after 28 days:

Abundance

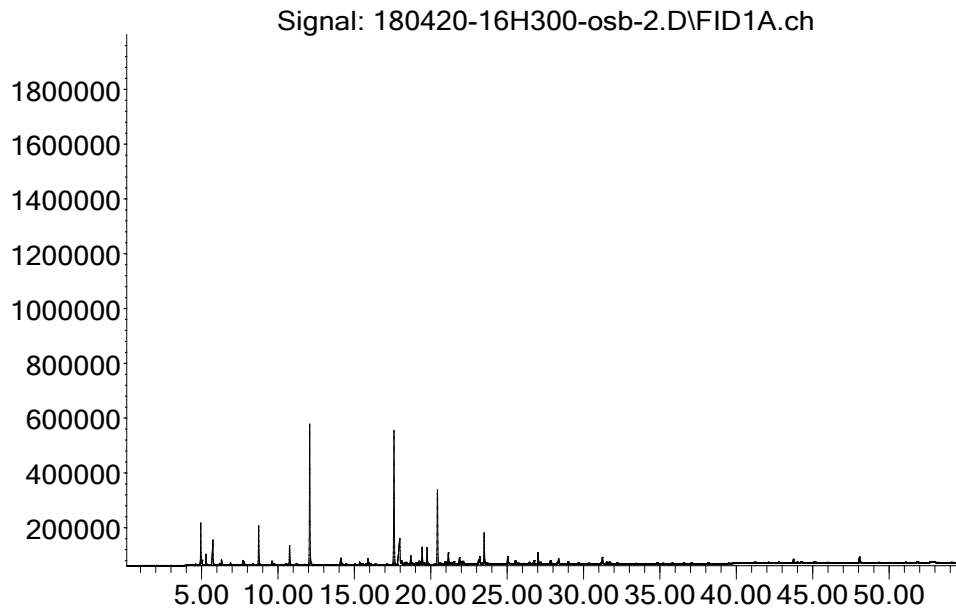

Time-->

TVOC between C<sub>6</sub> and C<sub>16</sub>, means compounds eluting between 6.5 and 38 minutes.

## Appendix 3

## Photo of the test specimen

